

Grain Coarsening Effects of Chromium and Iron in Au-Ag-Cu Alloys

D. Ott and Ch. J. Raub

Forschungsinstitut für Edelmetalle und Metallchemie, Schwäbisch Gmünd, West Germany

Chromium and iron in concentrations as low as 0.3-0.5 per cent have been found to cause a marked coarsening of the microstructure of 18 carat Au-Ag-Cu alloys on annealing. Where minimum grain growth during annealing is required, as in the fabrication of rings and chains, the concentrations of these metals should therefore be kept at a low level.

In the fabrication of carat gold jewellery the extent of working or deformation of Au-Ag-Cu alloys between annealing treatments is normally monitored, since if it is less than about 30 per cent with most alloy compositions then grain growth during even relatively mild annealing treatments may be excessive and weak coarse grained structures may develop (1). These form surface patterns ('orange peel' effect) on further working, and in extreme cases the grain boundaries which delineate these patterns may deepen with disastrous effects. High carat red alloys in particular must not be annealed after they have had only small deformation.

During a systematic investigation of the effects of various metals in small concentrations on the microstructures and properties of 18 carat red and yellow gold alloys we have discovered that exceptionally large grained structures also develop in Au-Ag-Cu alloys in the presence of iron or chromium even though the degree of deformation before annealing is as high as 70 per cent. The effect is especially pronounced in silver-containing yellow gold alloys.

The effects of concentrations of up to 0.5 per cent iron or chromium were studied. The experimental conditions were those outlined in the

Table, and the microstructures observed are illustrated in Figures 1-7.

With a final annealing treatment at 700°C for 1 hour, iron and chromium concentrations of as little as 0.3 per cent already had a significant effect on grain size. If these concentrations were increased to about 0.5 per cent very coarse grains were observed. Figures 1-3 illustrate the latter effects.

If the final annealing treatment was at 800°C for 1 hour, as may often happen in practice, the deleterious effects of chromium and iron additions showed up (see Figures 4-6) even more clearly. Whereas 0.3 per cent iron or chromium increased the grain size by a factor of about 2, higher concentrations caused extreme grain growth (Figure 7).

No theoretical explanation of these effects can be given at this stage. It will be apparent, however, that they are important for gold jewellery manufacturers. Iron in particular is an element which can easily be introduced into alloys by remelting scrap or by bad refining. If alloys contaminated in this way are annealed during fabrication under the conditions found effective for uncontaminated alloys, coarse grained structures are likely to develop and give rise to production difficulties.

To ensure reproducibility of the properties of alloys used in production, especially of such articles as rings and chains in which a coarse structure is a disadvantage, it is therefore advisable that the iron and chromium concentrations in the alloys should be kept at a low level, and preferably below 0.1 per cent.

Acknowledgements

We wish to thank the Chamber of Mines of South Africa and the International Gold Corporation for supporting the research program during the course of which the above effects were observed.

Reference

1 O. Loebich, *Z. Metallk.*, 1953, **44**, 288-292

Table
Experimental Conditions

Alloy comp. (weight %)	Au, 75% Ag, 12.5% Fe or Cr, 0.0-0.5%; Cu, the remainder
Pre-treatments	(a) Cast, 70% deformed (b) Annealed at 700°C or 800°C for 1 hr, 70% deformed (c) Final annealing treatment as given in the captions to Figs. 1-7.

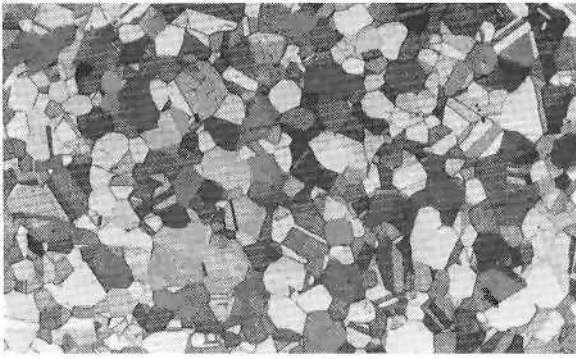


Fig. 1 18 carat yellow gold, annealed 1 hour, 700°C, × 100



Fig. 2 18 carat yellow gold + 0.5% Fe, annealed 1 hour, 700°C, × 100

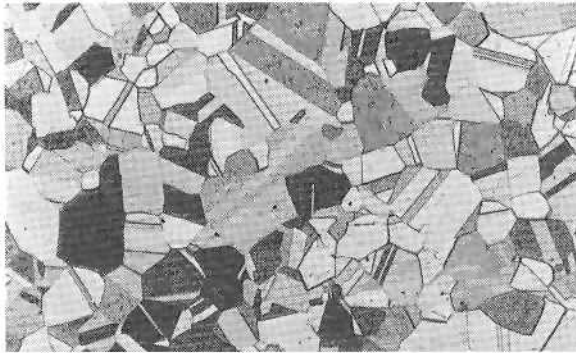


Fig. 3 18 carat yellow gold + 0.5% Cr, annealed 1 hour, 700°C, × 100

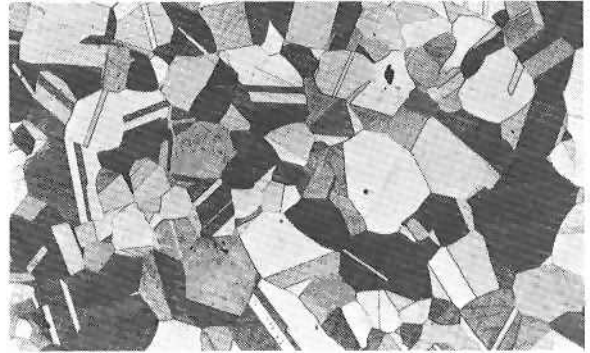


Fig. 4 18 carat yellow gold, annealed 1 hour, 800°C, × 100

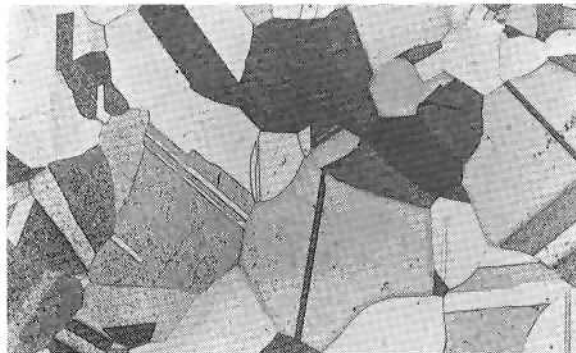


Fig. 5 18 carat yellow gold + 0.3% Fe, annealed 1 hour, 800°C, × 100

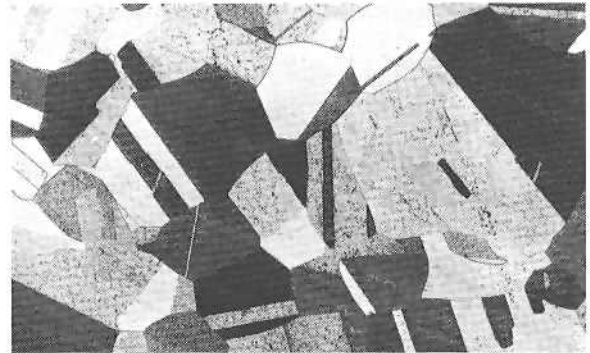


Fig. 6 18 carat yellow gold + 0.3% Cr, annealed 1 hour, 800°C, × 100

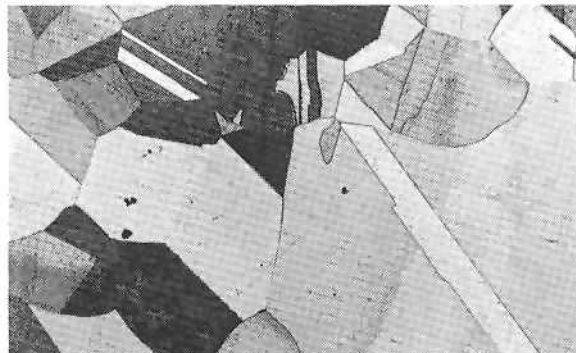


Fig. 7 18 carat yellow gold + 0.5% Fe, annealed 1 hour, 800°C, × 100

The marked effects of chromium and iron upon grain growth during the annealing of an 18 carat yellow gold (see Table) will be apparent from Figures 1-7
